


HP 3D High Reusability (HR) PA 12 FR, enabled by Evonik

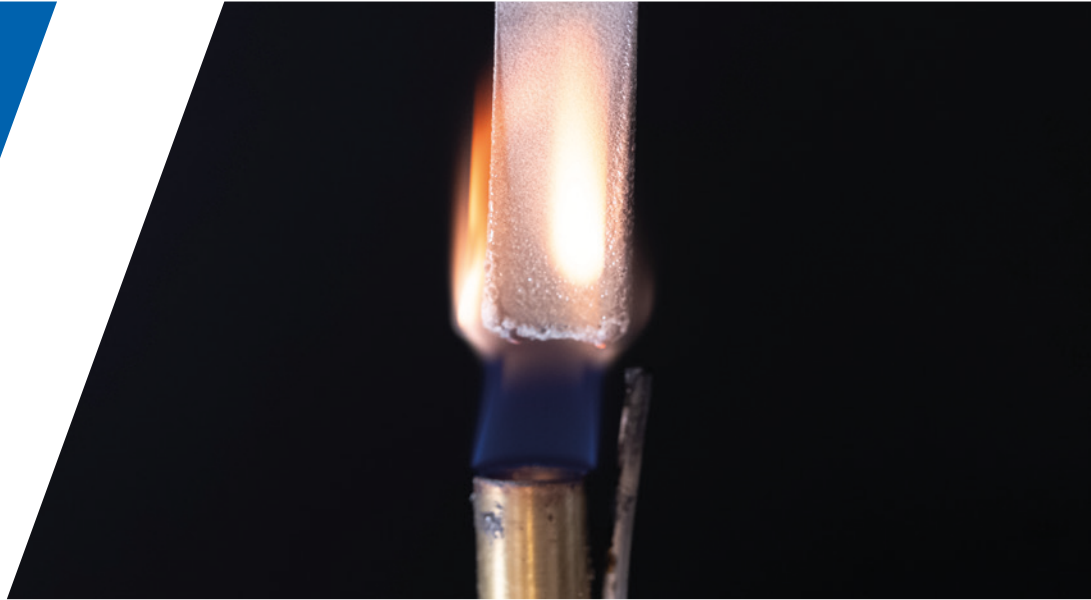

Halogen-free Flame Retardant (FR) material with 60% reusability,¹ disruptive cost per part,² and smooth surface finish.³

Flame Retardant

Halogen-free material,⁴ UL94 certified.⁵

- Made with halogen-free chemicals.⁴
- Achieves UL94 V0 flammability safety standard at 2.5 mm thickness.⁵
- PA12 particles encapsulated with FR particles provide homogenous flammability across parts.

60% reusability¹

Maximize powder efficiency with a 60% reusability ratio.¹

- Disruptive cost per part: Reduce variable cost per part and your total cost of ownership.²
- Minimize waste while balancing performance and reusability.
- Reduced carbon footprint: Manufactured using renewable energy sources and biomethane for polymer production.⁶

Premium quality

Produce quality parts with premium surface aesthetics.

- Smooth surface: Achieve premium surface aesthetic parts directly from the printer that are up to 60% smoother.⁷
- Isotropic properties: Produce functional prototypes and final parts with fine detail and dimensional accuracy across a variety of applications.

General properties

Reusability	60%		
	Value	Unit	Method
Part density	1.13	g/cm³	ASTM D792
Melting temperature	187	°C	DSC analysis
Powder melting point (DSC)	187 / 369	°C / °F	ASTM D3418
Particle size	55	µm	ASTM D3451
Bulk density of powder	0.47 / 0.017	g/cm³ / lb/in³	ASTM D1895
Table 1. General material properties for HP HR PA 12 FR, enabled by Evonik			

Mechanical properties⁸

	Orientation	Value	Unit	Method
Tensile Strength ⁹	XY	46	MPa	ASTM D638
	Z	46		
Tensile Modulus ¹⁰	XY	2580	MPa	ASTM D638
	Z	2540		
Elongation at Break ¹¹	XY	4.7	%	ASTM D638
	Z	4		
Elongation at Yield	XY	3.8	%	ASTM D638
	Z	3.6		
Izod Impact Notched ¹²	XY	2.8	kJ/m ²	ASTM D256
	Z	2.7		
Heat Deflection Temperature 0.45 MPa	XY	172	°C	ASTM D648
	Z			
Heat Deflection Temperature 1.82 MPa	XY	97	°C	ASTM D648
	Z			
Ball pressure	XY and Z	165	°C	IEC 60695
Table 2. Mechanical properties for HP HR PA 12 FR, enabled by Evonik				



Electrical properties

	Orientation	Value	Unit	Method
Comparative Tracking Index (CTI)	XY	408	V	ASTM D3638
	Z	423		
Dielectric Strength (Conditioning 48 h / 23 °C / 50% RH)	XY	7.6	kV/mm	ASTM D149
	Z	6.7		
Dielectric Strength (Conditioning 96 h / 35 °C / 90% RH)	XY	2.5	kV/mm	ASTM D149
	Z	1.9		
Volume Resistivity at 23 °C / 50% RH	XY	4.96E+13	Ω·cm	ASTM D257
	Z	5.71E+13		
Surface Resistivity at 23 °C / 50% RH	XY	9.74E+14	Ω	ASTM D257
	Z	1.03E+15		

Table 3. Electrical properties for HP HR PA 12 FR, enabled by Evonik

Flammability properties

		UL 94 (Blue Card available)			High-Current Arc Ignition (HAI)			Hot Wire Ignition (HWI)		
Thick-ness	Orienta-tion	Value	Unit	Method	Value	Unit	Method	Value	Unit	Method
1 mm	XY and Z	HB	Pass	UL 94	PLC 0	Pass	UL 746A	PLC 4	Pass	UL 746A
1.8 mm	XY and Z	V2	Pass		PLC 0	Pass		PLC 2	Pass	
2.5 mm	XY and Z	V0	Pass		PLC 0	Pass		PLC 1	Pass	

Table 4. UL results for HP HR PA 12 FR, enabled by Evonik

		Glow Wire Flammability Index (GWFI)			Glow Wire Ignition Test (GWIT)		
Thickness	Orientation	Value	Unit	Method	Value	Unit	Method

Please reach out to an HP representative for test results.

Railway	Thickness	Value	Unit	Method	
R22	1.4 mm	HL2	Pass	EN 45545-2	
	1.4 mm to 10 mm	HL1			
R23	1.4 mm to 10 mm	HL2	Pass		
R24	1.4 mm to 10 mm	HL2	Pass		

Table 5. EN45545 results for HP HR PA 12 FR, enabled by Evonik



Dimensional accuracy results

Performance results for the HP 3D HR PA 12 FR, enabled by Evonik, (BALANCED PA12 FR print mode)

The following results were based on internal testing using the Test Job. Results may vary with other jobs and geometries. Testing was performed for HP 3D HR PA 12 FR with a 60% refresh ratio using the PA 12 FR Balanced print profile, natural cooling, and measured after bead-blasting with glass beads at 5-6 bars. All HP-recommended printer setup and adjustment processes were following and printheads were aligned.

This table shows the dimensional tolerances obtained during the characterizations of the Test Job for a target process capability of cpk1.33 (4 sigma)

Tolerances for $C_{pk} = 1.33^{i,ii,iii}$ (in mm)	Nominal dimension					
	0 - 30 mm		30 - 50 mm		50 - 80 mm	
	XY	Z	XY	Z	XY	Z
With the general dimensional profile for the HP Jet Fusion 5600 Series 3D Printing Solution	±0.20	±0.42	±0.25	±0.50	±0.30	±0.60
i. Based on internal testing and measured using the "HP dimensional capability characterization job". Results may vary with other jobs and geometries. ii. Using HP 3D HR PA 12 FR, enabled by Evonik material, 60% refresh ratio. Balanced PA 12 FR print profile, natural cooling, and measured after bead-blasting with glass beads at 5-6 bars. iii. Following all HP-recommended printer setup and adjustment processes and printheads aligned using semi-automatic procedure.						
Table 6. Dimensional capabilities for HP 3D HR PA 12 FR, enabled by Evonik. Target process capability of $C_{pk} = 1.33$						

This table shows the dimensional tolerances obtained during the characterizations of the Test Job for a target process capability of cpk1.00 (3 sigma)

Tolerances for $C_{pk} = 1.00^{i,ii,iii}$ (in mm)	Nominal dimension					
	0 - 30 mm		30 - 50 mm		50 - 80 mm	
	XY	Z	XY	Z	XY	Z
With the general dimensional profile for the HP Jet Fusion 5600 Series 3D Printing Solution	±0.15	±0.34	±0.18	±0.40	±0.22	±0.47
i. Based on internal testing and measured using the "HP dimensional capability characterization job". Results may vary with other jobs and geometries. ii. Using HP 3D HR PA 12 FR, enabled by Evonik material, 60% refresh ratio. Balanced PA 12 FR print profile, natural cooling, and measured after bead-blasting with glass beads at 5-6 bars. iii. Following all HP-recommended printer setup and adjustment processes and printheads aligned using semi-automatic procedure.						
Table 7. Dimensional capabilities for HP 3D HR PA 12 FR, enabled by Evonik. Target process capability of $C_{pk} = 1.00$						

Ordering information*

Product number	Material
AN5S8A	HP 3D HR PA12 FR enabled by Evonik 300L/130 kg Material
AN5S9A	HP 3D HR PA12 FR enabled by Evonik 300L/130 kg Production Material
AN5T0A	HP 3D HR PA12 FR enabled by Evonik 1400L/600 kg Material
Table 8. Ordering information for HP 3D HR PA 12 FR	

* Only available for the HP Jet Fusion 5600 Series 3D Printing Solution.

1. HP Jet Fusion 5600 Series 3D Printing Solutions using HP 3D High Reusability PA 12 FR, enabled by Evonik, provide 60% powder reusability ratio, producing functional parts batch after batch. For testing, material is aged in real printing conditions and powder is tracked by generations (worst case for reusability). Parts are then made from each generation and tested for mechanical properties and accuracy.

2. Based on internal testing and public data for solutions on market as of March 2025. Cost analysis based on: standard solution configuration price, supplies price, and maintenance costs recommended by manufacturer. Cost criteria: printing 2 full build chambers of parts per week over 1 year of 41 cm³ parts at 8% packing density on Balanced print mode using HP 3D High Reusability PA 12 FR material on HP Jet Fusion 5600 Series 3D Printing Solutions, and the powder reusability ratio recommended by manufacturer, and printing under certain build conditions and part geometries.

3. Compatible with HP Jet Fusion 5600 Series 3D Printing Solutions.

4. This flame retardant is non-halogenated according to IEC 61249-2-21, based on Evonik material composition as of January 2025.

5. Based on testing done by UL and reported on UL blue card on March, 2025.

6. Based on carbon emissions calculations comparing HP 3D HR PA 12 FR, enabled by Evonik material with a theoretical version of the same material manufactured with non-renewable energy sources.

7. Based on internal HP testing for Linear Surface roughness (Ra). HP tested 5 copies using HP 3D HR PA 12, enabled by Evonik and HP 3D HR PA 12 FR, enabled by Evonik (both using Balanced print mode) with the HP Jet Fusion 5600 series 3D Printing Solution and post processed with sandblasting. Tested all 5 faces of the printed part.

8. Based on internal testing and measured using the "HP Half Commercial Datasheet Job" and 2 material lots following material quality control guidelines. Results may vary with other geometries, jobs, material lots, and material conditions. Using HP 3D HR PA 12 FR, enabled by Evonik, Balanced print profile, natural cooling, and measured after bead-blasting with glass beads at 5-6 bars. Following all HP-recommended printer setup and adjustment processes and printheads aligned. Tensiles measured within 40h to 170h of being printed.

9. 95% of measured tensiles show Tensile Strength above 38 Mpa.

10. 95% of measured tensiles show Modulus values between 2250 to 2850 MPa.

11. 95% of measured tensiles show Elongation at Break in XY-direction above 3.5% and Elongation at Break in Z-direction above 3%.

12. Using the Izod test method A with notched at 3.2 mm specimen according to the ASTM D256 standard.